

Direct Observation of Antiferro-Quadrupolar Ordering – Resonant X-ray Scattering Study of DyB_2C_2 –

K.Hirota^{1,4}, N.Oumi¹, T.Matsumura^{1,4}, H.Nakao^{2,4}, Y.Wakabayashi^{2,3}, Y.Murakami^{2,4}, and Y.Endoh^{1,4}

¹Department of Physics, Tohoku University, Sendai, 980-8578 Japan

²Photon Factory, Institute of Materials Structure Science, KEK, Tsukuba 305-0801, Japan

³Department of Physics, Keio University, Yokohama 223-8522, Japan

⁴CREST, Japan Science and Technology Corp., Tsukuba 305-0047, Japan

(February 1, 2008)

Antiferroquadrupolar (AFQ) ordering has been conjectured in several rare-earth compounds to explain their anomalous magnetic properties. No direct evidences for AFQ ordering, however, have been reported. Using the resonant x-ray scattering technique near the Dy L_{III} absorption edge, we have succeeded in observing the AFQ order parameter in DyB_2C_2 and analyzing the energy and polarization dependence. Much weaker coupling between orbital degrees of freedom and lattice in $4f$ electron systems than in $3d$ compounds provides an ideal platform to study orbital interactions originated from electronic mechanisms.

PACS numbers: 61.10.-i, 71.20.g, 75.25.+z

Magnetic ions in a highly symmetrical crystalline may have an orbital degeneracy in the crystalline electric field (CEF) ground state. With decreasing temperature, this degeneracy becomes lifted by some interactions. A typical example is the cooperative Jahn-Teller (JT) distortion, [1] where the *orbital degrees of freedom*, coupled with lattice distortion, gives rise to a structural phase transition to lower crystalline symmetry. Long range orbital ordering (OO) thus driven was confirmed in KCu_2F_4 by polarized neutron scattering [2] and in LaMnO_3 by resonant x-ray scattering. [3] Although OO is not necessarily associated with the cooperative JT distortion as reported in $\text{La}_{0.88}\text{Sr}_{0.12}\text{MnO}_3$, [4] coupling with other degrees of freedom such as charge or lattice would remain in $3d$ compounds. [5,6]

In $4f$ electron systems with degenerated ground state, however, orbital degrees of freedom may remain and undergo a phase transition without structural distortion because of much weaker coupling between lattice and well-localized $4f$ orbitals. Such a possibility was first discussed in cubic CeB_6 as long range ordering of electric quadrupole moments of $4f$ orbitals. [7] Quadrupole ordering is defined as a phenomenon that f electron charge distribution *which diagonalizes certain quadrupole moments* orders spontaneously and spatially as lowering temperature. In ferroquadrupole (FQ) arrangement, aligned quadrupole moments uniformly distort the lattice through a linear coupling between quadrupole moment O_Γ at the wave vector $q = 0$ and strain ϵ_Γ in the same symmetry. Therefore, the order parameter can be obtained by measuring JT-like lattice distortion. [8] In antiferroquadrupole (AFQ) arrangement, however, the AFQ order parameter at $q \neq 0$ does not linearly couple with the uniform strain. Thus, atomic displacement is not always expected, which makes it extremely difficult to observe the order parameter.

In this Letter, we present the first direct evidence for

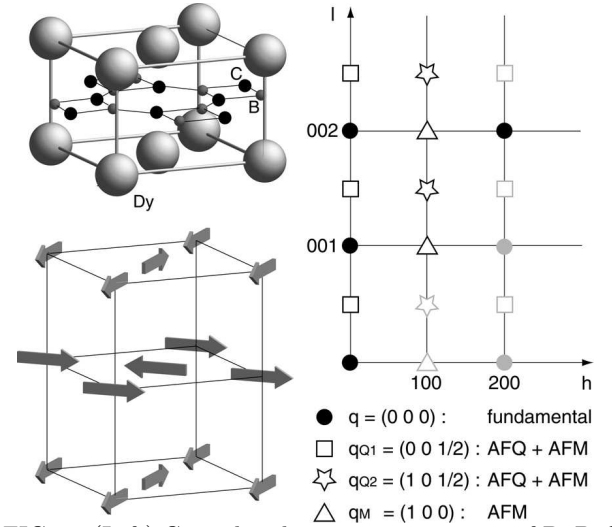


FIG. 1. (Left) Crystal and magnetic structures of DyB_2C_2 ($P4/mbm$: $a = 5.341 \text{ \AA}$, $c = 3.547 \text{ \AA}$ at 30 K). (Right) Schematic view of q -space investigated.

AFQ ordering by the resonant x-ray scattering study of DyB_2C_2 near the Dy L_{III} absorption edge. As shown in Fig. 1, DyB_2C_2 has the $P4/mbm$ tetragonal structure consisting of Dy layers and B-C networks stacking alternately along the c direction. [9] Covalently bonded B-C network requires no electron transfer from Dy^{3+} ions ($4f^9$, $^6H_{15/2}$), thus DyB_2C_2 has three conduction electrons per formula in the $5d$ band and is metallic. [10,11]

Recently, Yamauchi *et al.* [9] reported that DyB_2C_2 exhibits phase transitions at $T_Q \sim 25 \text{ K}$ and $T_N \sim 16 \text{ K}$. Specific heat measurement showed two distinct λ -type anomalies at T_Q and T_N , each of which releases the entropy equivalent to $R \ln 2$. Since Dy^{3+} is a Kramers ion, two Kramers doublets should be involved in these successive transitions. It is thus expected that the ground and first excited Kramers states are close or nearly degenerated and that quadrupole degrees of freedom remain. In

contrast to the specific heat, almost no anomaly was observed in the magnetic susceptibility at T_Q and no structural transition nor lattice distortion were confirmed at T_Q and T_N . Thus, the transition at T_Q is neither magnetic nor structural. Neutron diffraction revealed antiferromagnetic (AFM) ordering below T_N . Spins are aligned within the c plane and the magnetic structure is basically described with two propagation vectors $[1\ 0\ 0]$ and $[0\ 1\ \frac{1}{2}]$, indicating that Dy magnetic moments realize 90° arrangement along c , which is hardly explained only by magnetic interactions. They also found weak magnetic signals at $[0\ 0\ 0]$ and $[0\ 0\ \frac{1}{2}]$, indicating that moments are slightly canted within the c plane. From these results, they proposed that the phase I ($T > T_Q$) is paramagnetic, the phase II ($T_N < T < T_Q$) is the AFQ ordered phase, and the phase III ($T < T_N$) is the AFM and AFQ ordered phase.

We have grown a DyB_2C_2 single crystal by the Czochralski method. The crystal was checked by powder x-ray diffraction, which shows a diffraction pattern consistent with Ref. [9] and no detectable foreign phases. The temperature dependence of magnetization is also in good agreement. X-ray scattering measurements were performed on a six-axis diffractometer at the beamline 16A2 of the Photon Factory in KEK. A piece of the sample (~ 2 mm cubic) was mounted in a closed cycle ^4He refrigerator so as to align the c -axis parallel to the ϕ axis of the spectrometer. The mosaicness was about 0.07° FWHM. The azimuthal angle Ψ (rotation around the scattering vector) is defined as 0° where the scattering plane contains the b axis, i.e., $[0\ 1\ 0]$. The incident energy was tuned near the Dy L_{III} edge, which was experimentally determined to be 7.792 keV using fluorescence. To separate the linearly polarized σ' ($\perp$ the scattering plane) and π' ($\parallel$ the scattering plane) components of diffracted beam, we used the PG (006) reflection, which scattering angle is about 91° at this energy resulting in almost complete polarization: the $\sigma - \pi'/\sigma - \sigma'$ intensity ratio at $(0\ 0\ 2)$ was less than 0.5 %. In our configuration, $(0\ 0\ 2)$ intensity at Dy L_{III} for $\sigma - \sigma'$ is $\sim 2.5 \times 10^6$ counts per second (cps) when the ring current is 300 mA.

AFQ ordering will be directly observed by exploiting the sensitivity of x-ray scattering to an anisotropic f electron distribution. In the present study, we have utilized the ATS (anisotropic tensor of x-ray susceptibility) technique, which was originally developed for detecting “forbidden reflections” which appear due to the asphericity of atomic electron density. [12,13] The ATS reflections, which are usually very small, would increase in the resonant x-ray scattering near an absorption edge because the anomalous scattering factor, sensitive to an anisotropic charge distribution, is dramatically enhanced. This technique was successfully applied to the OO phenomena in 3d oxides. [3,4,5,6] We thus tuned the incident energy of x-rays at Dy L_{III} , where $2p_{3/2} \rightarrow 5d_{5/2}$ dipole and $2p_{3/2} \rightarrow 4f_{7/2}$ quadrupole transitions are expected.

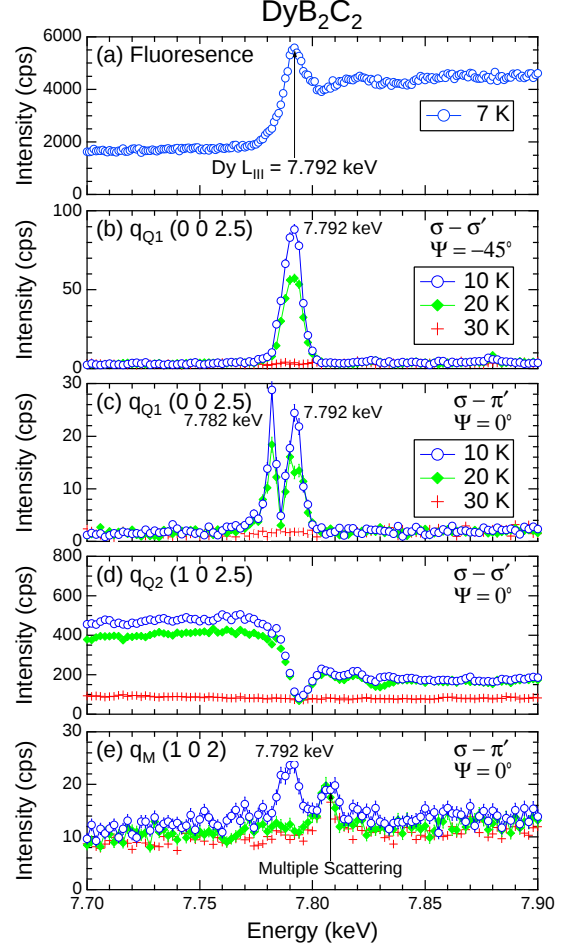


FIG. 2. Incident energy dependences of (a) fluorescence (unpolarized), (b) q_{Q1} peak at $(0\ 0\ 2.5)$ for $\sigma - \sigma'$ polarization, (c) $(0\ 0\ 2.5)$ for $\sigma - \pi'$, (d) q_{Q2} peak at $(1\ 0\ 2.5)$ for $\sigma - \sigma'$, and (e) q_M peak at $(1\ 0\ 2)$ for $\sigma - \pi'$. No background subtraction was made.

Figure 1 shows a schematic view of investigated q -space. Fundamental reflections appear where $h + k = \text{even}$. To look for the AFQ and AFM order parameters, we made scans along $(0\ 0\ l)$, $(\frac{1}{2}\ 0\ l)$, $(1\ 0\ l)$, $(h\ 0\ 2)$, $(\frac{1}{2}\ \frac{1}{2}\ l)$, $(1\ 1\ l)$ and $(2\ 1\ l)$ at Dy L_{III} and making no polarization analysis. Scans at 30 K give only fundamental reflections. At 20 K ($< T_Q$), two kinds of superlattice reflections appear; one is characterized by a propagation vector $q_{Q1} = (0\ 0\ \frac{1}{2})$ and the other is by $q_{Q2} = (1\ 0\ \frac{1}{2})$. At 10 K ($< T_N$), additional reflections appear at forbidden reflection points which propagation vector is $q_M = (1\ 0\ 0)$. These temperature dependences suggest that the q_{Q1} and q_{Q2} reflections correspond to the expected AFQ ordering and that the q_M peak is the AFM order parameter.

Figure 2 shows the incident energy dependences of fluorescence as well as $(0\ 0\ 2.5)$, $(1\ 0\ 2.5)$ and $(1\ 0\ 2)$ reflections, i.e., q_{Q1} , q_{Q2} and q_M points. The $(0\ 0\ 2.5)$ peak shows a sharp enhancement at Dy L_{III} in both $\sigma - \sigma'$ and

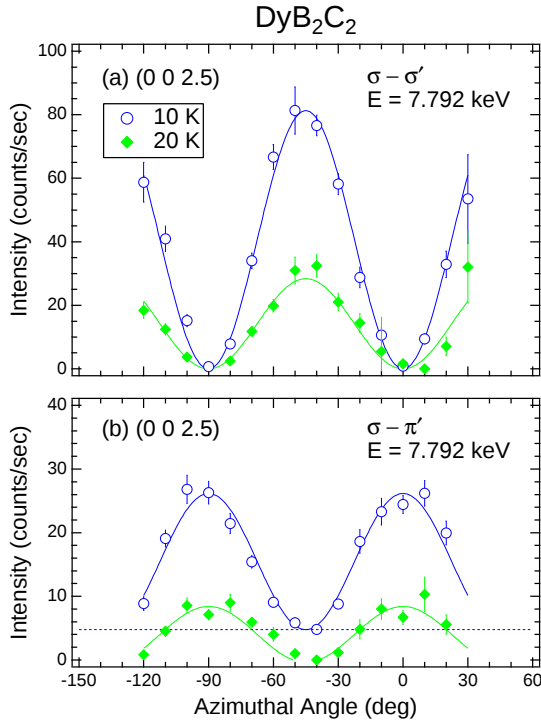


FIG. 3. Azimuthal dependences of a q_{Q1} peak (0 0 2.5) for $\sigma - \sigma'$ and $\sigma - \pi'$ polarizations. $\omega - 2\theta$ scan was made at each azimuthal angle after lining up the crystal using (0 0 2). Intensity was obtained by fitting a Gaussian to the peak profile. The peak width of (0 0 2.5) shows no particular Ψ dependence and no difference from that of (0 0 2), i.e., the instrumental resolution. The solid curve is proportional to $\sin^2 2\Psi$.

$\sigma - \pi'$ processes. Note that there exists another enhancement for $\sigma - \pi'$ at 7.782 keV, 10 eV lower than the Dy L_{III} edge, which we speculate corresponds to level splitting within $2p$ and $5d$ states or a quadrupole transition. The (1 0 2) peak shows an enhancement in $\sigma - \pi'$ at the Dy L_{III} edge at 10 K. No such enhancement was found in $\sigma - \sigma'$ at (1 0 2), indicating that the (1 0 2) reflection is dominated by $\sigma - \pi'$ scattering, as expected for resonant magnetic scattering. As for (1 0 2.5), there exists a clear energy enhancement in $\sigma - \pi'$ at Dy L_{III} below T_N indicating magnetic contribution, which is consistent with Ref. [9]. On the contrary, the $\sigma - \sigma'$ scattering exhibits *non-resonant* reflection below T_Q as shown in Fig. 2(d). We first focus upon the resonant peaks, then discuss this non-resonant contribution at (1 0 2.5).

In addition to the enhancement, it is expected that the resonant ATS scattering from AFQ ordering shows the azimuthal angle dependence reflecting the shape of f electron distribution. As shown in Fig. 3, we measured azimuthal dependence for two different polarizations by rotating the crystal around the scattering vector kept at (0 0 2.5). Figure 3 demonstrates that the $\sigma - \sigma'$ scattering exhibits a characteristic four-fold oscillation, compatible to the tetragonal symmetry. The intensity approaches zero at $\Psi = 0$ and $\frac{\pi}{2}$. The $\sigma - \pi'$ scattering of (0 0 2.5)

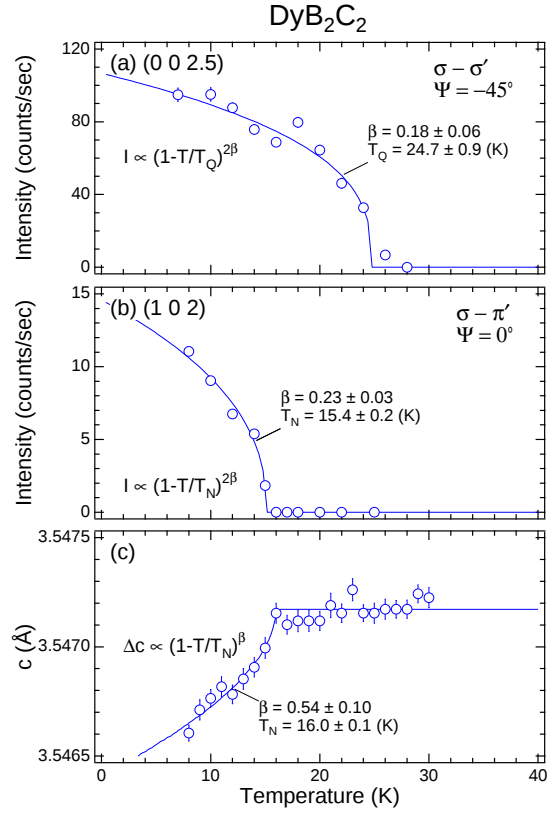


FIG. 4. Temperature dependences of (a) AFQ and (b) AFM order parameters. Peak profiles were obtained at particular polarization and azimuthal conditions so as to maximize the intensities for (0 0 2.5) and (1 0 2), and fitted well to a Gaussian. Peak widths are resolution limited in the temperature range where peaks are visible in our counting statistics (10 – 15 seconds per point). (c) Temperature dependence of spontaneous strain Δc estimated using (0 0 2).

also shows a four-fold oscillation. However, the oscillation for $\sigma - \pi'$ is reversed to that of $\sigma - \sigma'$. Plus, the intensity minimum remains finite at 10 K and approaches zero at 20 K, indicating that there exists a magnetic contribution to the $\sigma - \pi'$ scattering at (0 0 2.5), which is consistent with Ref. [9]. These azimuthal dependences strongly indicate the existence of anisotropic f electron distribution and the associated AFQ ordering below T_Q .

Figures 4 show the order parameters measured at (0 0 2.5) and (1 0 2) as well as the spontaneous strain Δc estimated from the (0 0 2) peak position. The order parameters behave as continuous 2nd order transitions and can be fitted to power laws indicated in the figures. The transition temperatures thus obtained are in good agreement with the values reported by Yamauchi *et al.* [9]. The critical exponents β obtained for the AFQ ordering and AFM ordering are about 0.2. The spontaneous strain Δc has the β value close to 0.5, which is twice as much as that of the AFM ordering, indicating that Δc is a secondary order parameter and quadratically coupled to the AFM ordering. For quantitative discussions, we

need more statistics, which will not only give more precise β values but also provide more information such as correlation lengths above T_N and T_Q .

Note that no anomaly was found in Δc at T_Q , which implies that the quadrupole ordering has very weak coupling, if any, to the lattice of DyB_2C_2 . Since the superlattice peak at $(1\ 0\ 2.5)$ appearing below T_Q is non-resonant and has $\sigma - \sigma'$ polarization, it might be ascribed to atomic displacement. As a simple model for order estimation, let us assume that Dy ions are displaced along c and that the directions are alternated between nearest neighbors. From the intensity ratio below Dy L_{III} , $I(1\ 0\ 2.5)/I(0\ 0\ 2) = 4.0 \times 10^{-5}$, we obtain the displacement $\delta = 0.0014\ \text{\AA}$ ($0.00040\ c$). With this small atomic displacement, the change of lattice constant may not be detected by the present x-ray diffraction which resolution is $\Delta c/c \sim 10^{-4}$ (see Fig. 4(c)). Recently, Benfatto *et al.* [14] theoretically reexamined the resonant x-ray scattering study of LaMnO_3 [3] and argued that the resonant signal is mostly due to the JT distortion resulting in anisotropic Mn-O bond lengths. This is in contrast with another theoretical description by Ishihara and Maekawa, [15] who proposed a mechanism based upon the Coulomb interaction between $4p$ conduction band and the ordered $3d$ orbitals. In DyB_2C_2 , however, it is very unlikely that the lattice distortion results in the observed anisotropic electron distribution. It is still required to further study the $(1\ 0\ 2.5)$ reflection, including the azimuthal dependence, and to consider other possibilities such as asphericity of atomic electron density due to AFQ ordering.

Let us briefly discuss the CEF of DyB_2C_2 . Using the equivalent operator formalism, [16,17] we have constructed a point charge model, which shows that the ground ($J_z = \pm\frac{1}{2}$) and first excited ($J_z = \pm\frac{3}{2}$) Kramers doublets almost degenerate and are well separated from the other excited states. These results confirm the existence of a pseudo quartet ground state in which the orbital degrees of freedom remain, and are consistent with a strong planar magnetic anisotropy which aligns the magnetic moments within the c plane. [9] Details of the calculation will be published elsewhere. [18].

The present study unambiguously shows that the resonant scattering at q_{Q1} corresponds to the AFQ ordering. However, the mechanism yielding such resonant scattering is not completely understood. When allowed, the dipole transition usually overwhelms the quadrupole transition in resonant scattering. Similar to a d orbital angular momentum, a quadrupole moment has five elements, i.e., $Q_m^{(2)}$ ($m = 2, 1, 0, -1, -2$) where $Q_m^{(l)} = \int \rho(\mathbf{r}) \mathbf{r}^l \sqrt{4\pi/(2l+1)} Y_{lm}(\theta, \phi) d\mathbf{r}$ in the polar coordinate. In the CEF, the five elements are classified in a particular irreducible representation, which can be conveniently explained by the Stevens's equivalent operators [16]. In the cubic O_h symmetry, for example, they are propor-

tional to $O_2^0 = \{3J_z^2 - J(J+1)\}/\sqrt{3}$ and $O_2^2 = J_x^2 - J_y^2$ in the Γ_3 (e_g) symmetry, and $O_{xy} = J_x J_y + J_y J_x$, O_{yz} , and O_{zx} in the Γ_5 (t_{2g}) symmetry. Actual quadrupole moments can be obtained by calculating their expected values. Through a strong $c-f$ coupling between $5d$ conduction band and localized $4f$ orbitals, the AFQ ordering would be projected onto the $5d$ orbital states. To completely understand the present experimental results, it is necessary to establish much more detailed scattering mechanism in a proper CEF symmetry.

In conclusion, the present resonant ATS x-ray scattering study has directly shown the existence of long range AFQ ordering in DyB_2C_2 , which had been theoretically conjectured in some f electron systems, and given the order parameter and the information concerning the final polarization and azimuthal dependence, which are directly linked to the type of AFQ moments.

The authors are indebt to H. Yamauchi, H. Onodera and Y. Yamaguchi for sharing their experimental results and sample preparation techniques prior to publication. We also acknowledge N. Kimura for helping single crystal growth and T. Arima and S. Ishihara for crucial discussions. This work was supported by Core Research for Evolutional Science and Technology (CREST).

-
- [1] G. A. Gehring and K. A. Gehring, Rep. Prog. Phys. **38** 1 (1975).
 - [2] J. Akimitsu and Y. Ito, J. Phys. Soc. Japan **40**, 1621 (1976).
 - [3] Y. Murakami *et al.*, Phys. Rev. Lett. **81**, 582 (1998).
 - [4] Y. Endoh *et al.*, Phys. Rev. Lett. **82**, 4328 (1999).
 - [5] Y. Murakami *et al.*, Phys. Rev. Lett. **80**, 1932 (1998).
 - [6] L. Paolasini *et al.*, Phys. Rev. Lett. **82**, 4719 (1999).
 - [7] P. Morin and D. Schmidt, in *Ferromagnetic Materials*, Vol. 5, edited by K. H. J. Buschow and E. P. Wohlfarth (Elsevier Science, Amsterdam, 1990), p. 1.
 - [8] B. Lüthi, in *Dynamical Properties of Solids*, Vol. 3, edited by G. K. Horton and A. A. Maradudin (North-Holland, Amsterdam, 1980), p. 245.
 - [9] H. Yamauchi *et al.*, J. Phys. Soc. Japan **68**, 2057 (1999).
 - [10] J. Bauer and O. Bars, Acta Crystallogr. B **36** 1540 (1980).
 - [11] T. Sakai *et al.*, Solid State Commun. **40** 445 (1981).
 - [12] V. E. Dmitrienko, Acta Crystallogr. A **39**, 29 (1983).
 - [13] D. H. Templeton and L. K. Templeton, Acta Crystallogr. A **41**, 133 (1985); **41**, 365 (1985); **42**, 478 (1986).
 - [14] M. Benfatto *et al.*, Phys. Rev. Lett. **83**, 636 (1999).
 - [15] S. Ishihara and S. Maekawa, Phys. Rev. Lett. **80**, 3799 (1998), and Phys. Rev. B **58** 13449 (1998).
 - [16] K. W. H. Stevens, Proc. Phys. Soc. **A65**, 209 (1952).
 - [17] M. T. Huchings, Solid State Phys. **16** 108 (1953).
 - [18] T. Matsumura *et al.* (unpublished).